

## Structural and Optical Characterization of Chemically Synthesized Nanostructured Zinc Oxide Thin Film

<sup>1</sup>Akintunde Ayodeji, AJAYI, <sup>2</sup>Aderemi Babatunde ALABI, <sup>1</sup>Olutayo Wale ABODUNRIN, <sup>1</sup>Kazeem Adeleke MUSILIYU

<sup>1</sup>Department of Mathematical and Physical Sciences, Afe Babalola University, Ado-Ekiti, Nigeria

<sup>2</sup>Department of Physics, University of Ilorin, Ilorin, Nigeria.

\*Corresponding author: ayodejiajayijp@gmail.com

### Abstract

Zinc Oxide (ZnO) thin film has been synthesized using the chemical spray pyrolysis technique and ethylene glycol has been used as solvent during the synthesis. X-ray diffraction (XRD) results show cubic and tetragonal phases of ZnO and the grain size was calculated to be 2.57nm. Optical characterization reveals very high transmittance within the visible-ultraviolet region and a bandgap of 3.49 eV was obtained for ZnO thin film. Scanning Electron Microscopic (SEM) analysis showed a void-free non-homogenous surface.

**Keywords:** ZnO; Spray pyrolysis; Ethylene glycol; Grain size.

### INTRODUCTION


Zinc oxide (ZnO) has distinguished itself as an excellent, novel material in the fields of water engineering where it is applied as biomolecule in water purification (Deak *et al.*, 2019) and more importantly optoelectronics where it finds applications as semiconductor in thin film transistors (Goyal and Kachhwaha, 2012), light emitting diodes, ultraviolet spectra detector, gas detectors (Foo *et al.*, 2014) and solar cells (Kolodziejczak – Radzimska *et al.*, 2014; Hussein *et al.*, 2015; Muchuweni *et al.*, 2017). ZnO has a wide direct energy bandgap of about 3.37 eV, high thermodynamic stability, high optical transparency and environmentally benign properties, making it a good candidate for thin film solar cell fabrication (Muchuweni *et al.*, 2017). Due to the scarcity of indium, ZnO can be considered as a potential replacement of the popular indium titanium oxide (ITO) as transparent conducting oxides in solar cell (Werner *et al.*, 2015; Diwater *et al.*, 2016). It can also serve as replacement for cadmium sulphide (CdS) as n-layer in thin film heterojunction device since cadmium has been reported to cause health related issues in humans (Rahimzadeh *et al.*, 2017; Offor *et al.*, 2015). Several techniques, both physical and chemical, has been employed in the deposition of ZnO thin films. The techniques include, radio frequency (RF) sputtering (Vyas *et al.*, 2015; Stamate, 2019), thermal evaporation (Stamate, 2019; Faraj and Ibrahim, 2011), chemical vapour deposition (Hassan and Kashim, 2013), sol-gel (Konan *et al.*,

2019), electrodeposition (Kumar and Sasikumar, 2014), chemical bath deposition (Huang *et al.*, 2012; Thool *et al.*, 2014) and chemical spray pyrolysis (Tecaru *et al.*, 2010; Cho *et al.*, 2019). Spray pyrolysis stands out as a simple and low cost deposition technique which does not require a high vacuum environment. Spray pyrolysis promotes spherical morphology of films and narrow particle size distribution. The spray pyrolysis technique can be increased to industrial scale and is applicable over a large area. Stoichiometry can also easily be controlled in spray pyrolysis. Several parameters which includes drying temperature, spray rate, nozzle to target distance, precursor and solvent govern the properties of spray-deposited ZnO thin films (Rajeshmon, 2013; Jeyadheepan *et al.*, 2019). The influence of solvent on spray-deposited thin films is very crucial because, the residence time of microsized droplets in drying chamber is heavily dependent on vapor pressure of the solvent. Water, which has been the most popular solvent in preparing chemical solutions has a high vapour pressure. For most researchers, the need to add drops of acid into precursor solution usually arises due to formation of precipitates. In recent times, the influence of solvents on structural, optical and electrical properties of chemically synthesized ZnO thin films and nanoparticles has been reported though, a deeper explanation of how the solvents affect these properties has not been provided. In this work, ZnO thin film has been synthesized by spray pyrolysis technique using ethylene glycol as solvent for precursor preparation.

## MATERIALS AND METHODS

### Experimental details

Zinc precursor solution (0.025 M) was prepared by dissolving zinc acetate dihydrate ( $(\text{Zn}(\text{CH}_3\text{CO}_2)_2 \cdot 2\text{H}_2\text{O})$ ) in ethylene glycol ( $(\text{CH}_2\text{OH})_2$ ). The mixture was stirred for 60 minutes using magnetic stirrer. 30 ml of the solution was sprayed in open air on glass substrates that has been cleaned ultrasonically in acetone heated to 60°C centigrade. The spraying was done at a pressure of 60 psi, spray rate of 2ml per minute and spray to target distance was maintained at 28 cm. The substrate temperature was maintained at 300°C during the spraying. The spray pyrolysis experimental setup is home-assembled and is shown in Figure 1. The sample was allowed to cool to room temperature and later annealed in a muffled furnace at 300°C for 120 minutes. All reagents used in preparation of the mixture are analytical grade and were purchased from Sigma Aldrich.

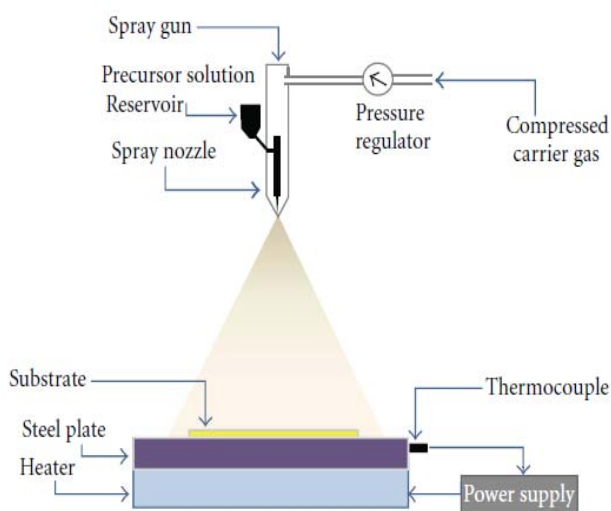

**Figure 1.** Schematic diagram of spray pyrolysis setup (Patil *et al.*, 2012).

### Characterization of ZnO thin films

The structural properties of synthesized ZnO thin film samples were studied using a Rigaku D/Max-IIIC X-ray diffractometer with a lynx eye detector using a copper target ( $\text{Cu}\alpha, 1.5418 \text{ \AA}$ ). All X-ray diffraction (XRD) data for the specimens were recorded at current and acceleration voltages of 25mA and 40 kV respectively. Surface morphology of the samples were studied by using Hitachi scanning electron microscope (SEM) and optical characterization was done using UV-vis spectrophotometer of CyberLab (model no. UV-100).


## RESULTS AND DISCUSSION

### Structural properties

The XRD pattern of ZnO is shown in figure 2. Peaks can be observed at  $2\theta$  equals 32.2°, 34.2°, 36.0°, 47.8°, and 56.0° which can be indexed to (100), (002), (101), (102), and (102) reflection planes of hexagonal wurzite ZnO. The peaks matched well with standard JCPDS pattern for ZnO (file number: 043-0002). Broadening of the peaks is an evidence of nanosized grains present in synthesized ZnO. The grain size was calculated from the (002) preferred orientation to be 2.57 nm. The Scherrer formula is written as

$$G = \frac{0.9\lambda}{\beta \cos\theta} \quad (1)$$

Where G is the grain size,  $\lambda$  is the  $\text{CuK}\alpha$ ,  $\beta$  is the full width at half maximum and  $\theta$  is the angle of diffraction. The results are in agreement with previous works that have reported cubic and hexagonal phases of ZnO (Chandappa and Venkatesha, 2012; Kumar *et al.*, 2014; Munoz-Aguirre *et al.*, 2019). The vapour pressure and polarity of the solvent may have been responsible for the nano-sized grains of the synthesized ZnO thin film. Ethylene glycol has very low vapour pressure and high dipole moment [34]. The low vapour pressure will increase the residence time of the microsized droplets during spraying which will prevent the droplets from drying too quickly, or blown away before it reaches the substrate. Relatively high grain sizes have been reported for ZnO thin films prepared by alcohol, deionized water or a mixture of both (Boukaous *et al.*, 2014; Benramache *et al.*, 2014; Bekkari *et al.*, 2019). We propose that a higher aggregate formation can be as a result of loose coiling of chemical bonds which causes a reduction in solvent polarity, and consequently, smaller aggregates are formed during thermal decomposition of solution, in which the solvent has higher dipole moment. The relationship between grain size and vapour pressure has been reported by Chin *et al.* (2019). The vapour pressure and dipole moment of some liquids that has been reported in literature on preparation of ZnO is shown in Table 1.

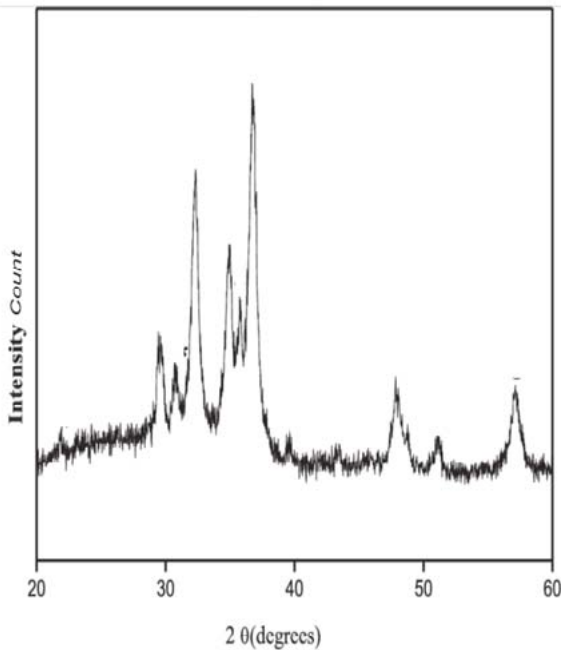

**Figure 2:** XRD patterns for ZnO thin film.

**Table 1.** Dipole moments and vapour pressures of solvents


Solvent	Dipole Moment (Debye)	Vapour Pressure (kPa)
Alcohol	1.660	5.950
Water	1.850	2.400
Ethylene Glycol	2.747	0.007

(Stamate, 2019; Patil et al., 2012).


**Optical properties**

The plot of transmittance and absorbance versus wavelength for ZnO thin film are shown in Figures 3 and 4. It can be observed that more than 80% transmittance was recorded within the ultraviolet – visible region. The smoothness of the curve and absence of interference pattern is an indication of homogeneity and low surface roughness of the film. A spike in the ultraviolet absorption edge from blueshift to redshift can be observed around 375 nm. The bend of the plot of absorbance versus wavelength can be observed at 350 nm. This observation is consistent with previous reports on the optical properties of ZnO (Tang et al., 2013; Foo et al., 2014; Marouf et al., 2017). The optical bandgap of ZnO thin film was calculated from the Tauc’s plot to be 3.49 eV and the plot is shown in figure 5. The plot is derived from equation 2.


$$(\alpha hf)^{1/n} = A(hf - E_g) \tag{2}$$

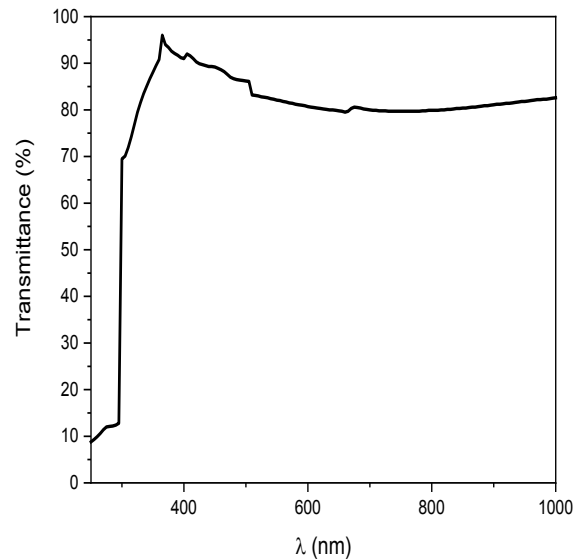

**Figure 3:** Transmission spectra of ZnO thin film

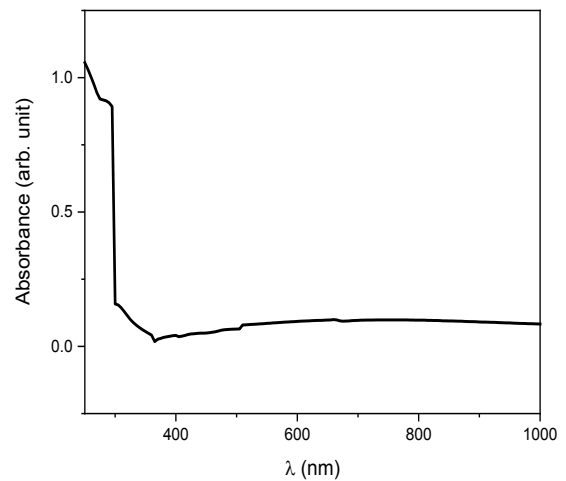

**Figure 4:** Absorption spectra of ZnO thin film

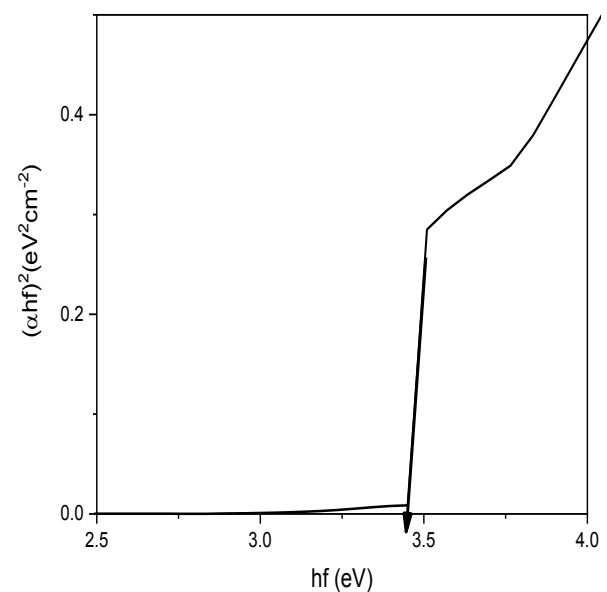


**Figure 5:** Optical bandgap of ZnO thin film.

### Morphological Properties


Flower like morphology can be observed in ZnO thin film shown in Figure 6. The SEM image shows a rough non-homogenous grains surface with voids absent. Flower shape morphologies have been reported in previous works on synthesis of ZnO that have shown the best optical response for solar cell applications (Stamate, 2019; Qiu et al., 2014).

### Compositional Analysis

The composition of the sprayed ZnO thin film layer was carried out by energy dispersive X-ray spectrophotometer and the EDX spectra is shown in Figure 7. The analysis showed the presence of zinc and oxygen in the ZnO thin film sample.

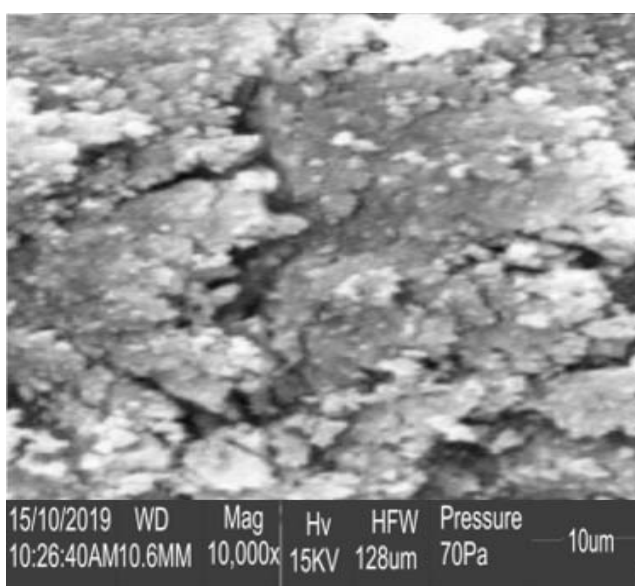

**Figure 6:** SEM micrograph of ZnO thin film.

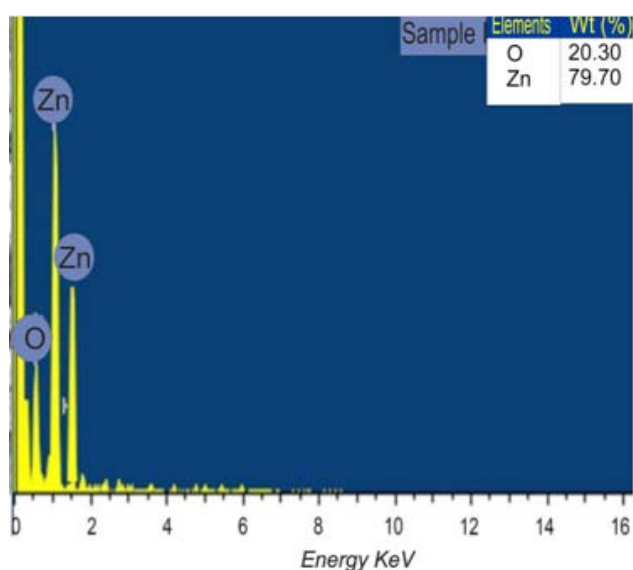

**Figure 7:** EDX spectra of ZnO thin film.

### Conclusion

ZnO thin film have been deposited using chemical spray pyrolysis technique using ethylene glycol as solvent. Cubic and tetragonal phases of ZnO were revealed by XRD study with the film having high orientation along the (002) direction. The small grain size is evidence that the synthesized ZnO thin film is nanostructured. The film exhibited very high transmittance and low absorbance within the visible-ultraviolet region of electromagnetic spectrum with a bandgap of 3.49 eV. SEM image revealed a surface free of voids.

### REFERENCES

- Bekkari, R., Jaber, B., Labrim, H., Ouafi, M., Zyyoun N. and Laanab, L. (2014). Effects of solvent and stabilizer molar ration on the growth orientation of sol-gel-derived ZnO thin films. *International Journal of Photoenergy*, 2019: 1-7.
- Benramache, S., Rahal, A. and Benhaoua, B. (2014). The effects of solvent nature on spray-deposited ZnO thin film prepared from  $Zn(CH_3COO)_2 \cdot 2H_2O$ . *Optik*, 125(2), 663 – 666.
- Biswas, M., Sharmin, M., Das, C., Poddar, J. and Choudary, S. (2016). Structural and Optical Characterization of magnesium doped zinc. *Dhaka University Journal of Science*, 64(1):1–6.
- Boukaous, C., Tella, A., Horwat, D., Aida, M.S., Boudine, B. and Ghanem, S. (2014). Influence of solvent on humidity sensing of sol-gel deposited ZnO thin film. *European Physical Journal of Applied Physics*, 65:20302.
- Chandrappa, K.G. and Venkatesha, T.V. (2012). Electrochemical Synthesis and Photocatalytic property of zinc oxide nanoparticles. *Nano-Micro*, 4(1):14–24.
- Chin, S., Choi, J.W., Woo, H.E., Kim J.H., Lee, H.S. and Lee, C.L. (2019). Realizing a highly luminescent perovskite thin film by controlling the grain size and crystallinity through solvent vapour annealing. *Nanoscale*, 11(13): 5775 – 6500.
- Cho, J., Hwang, S., Ko, D., and Chung, S. (2019). Transparent ZnO thin film deposited by spray pyrolysis for high-performance metal – oxide field effect transistors, *Materials*, 12(3423): 1 – 24.
- Deak, G., Dumitru, F.D., Moncea, M.A., Panait, A.M., Baraitaru, A.G., Olteanu, M.V., Boboc, M.G. and Stanciu, S. (2019). Synthesis of ZnO nanoparticles for water treatment applications. *International Journal of Conservation Science*, 10(2): 343 – 350.
- Diwate, K., Mohite, K., Shinde, M., Rodinya, S., Pawbake, A., Date, A., Pathan, H. and Jadkar, S. (2016). Synthesis and characterization of chemical spray pyrolyzed CZTS thin films for solar cell application. *Energy Procedia*, 110(2017): 180 – 187.



- Faraj, M.G. and Ibrahim, K. (2011). Optical and structural properties of thermally evaporated zinc oxide thin films on polyethylene terephthalate substrates. *International Journal of Polymer Science*, 2011: 1 – 4.
- Foo, K.L., Kashif, M., Hashim, U. and Liu, W. (2014). Effect of different solvents on the structural and optical properties of zinc oxide thin films for optoelectronic applications. *Ceramics International*, 40 (2014): 753 – 761.
- Foo, K.L., Kashif, M., Hashim, U. and Wei-Wen, L. (2014). Effect of different solvents on the structural and optical properties of zinc oxide thin film for optoelectronic applications, *Ceramics International*, 40(1):753 – 761.
- Fouad, O.A., Ismail, A.A., Zaki, Z.I. and Mohamed, R.M. (2006). Zinc oxide thin films prepared by thermal evaporation deposition and its photocatalytic activity. *Applied Catalysis*, 62(2006): 144 – 149.
- Goyal, A. and Kachhwaha, S. (2012). ZnO thin film preparation by spray pyrolysis and electrical characterization. *Materials Letters*, 68 (2012): 354 – 356.
- Hassan, N.K. and Kashim, M.R. (2013). Structural and optical properties of ZnO thin film prepared by oxidation of Zn metal powders. *Sains Malaysiana*, 42(2): 193 – 196.
- Huang, W., Hsieh, T. and Chu, A. (2012). Preparation of ZnO membrane by chemical bath deposition method via regulated acidity. *Journal of Information Engineering and Applications*, 2(5): 1 – 34.
- Hussein, B., Ebong, A. and Ferguson, I. (2015). Zinc oxide as an active n-layer and antireflection coating for silicon based heterojunction solar cell. *Solar Energy Materials and Solar Cells*, 139 (2015): 95 -100.
- Jeyadheepan, K., Karthick, P. and Sanjeeviraja, C. (2019). Development of automated spray pyrolysis setup for chemical vapour deposition like growth of thin solid films, *Journal of Instrumentation*, 14:PO4002.
- Kolodziejczak – Radzimska, A. and Jesionoskwi, T. (2014). Zinc-Oxide – From synthesis to applications: A review. *Materials*, 7(2014): 2833 – 2881.
- Konan, F.K., Hartiti, B. and Nkuissi, H.J. (2019). Optical-structural characterization of i-ZnO thin films deposited by chemical route. *Journal Materials and Environmental Sciences*, 10(10): 1003 – 1010.
- Kumar, M. and Sasikumar, C. (2014). Electrodeposition of Nanostructured ZnO thin films: A review. *American Journal of Materials Science and Engineering*, 2(2): 18 – 23.
- Kumar, N.S., Bangera, K.V. and Shivakumar, G.K. (2014). Effect of annealing on the properties of zinc oxide nanofiber thin films grown by spray pyrolysis technique. *Applied Nanoscience*, 4 (2): 209 – 216.
- Lupan, O., Postica, V., Grottrup, J., Mishra, A.K., de Leeuw, N.H., Carreira, J.F., Rodriguez, J., Ben-Sedrine, S., Correia, M.R., Monteiro, T., Cretu, V., Tiginyanu, I., Smazna, D., Mishra, Y.K. and Adelung, R. (2017). Hybridization of zinc oxide tetrapods for selective gas sensing applications. *ACS Applied Materials and Interfaces*, 9(4): 4084 – 4099.
- Marouf, S., Beniache, A. Guessasa, H., and Azizi, A. (2017). Morphological, structural and optical properties of ZnO thin films deposited by dip coating method *Materials Research*, 20(1): 88-95
- Minteer, S.D. (2011). *Handbook of Biofuels Production*, Woodhead Publishing Series in Energy, 258 – 265.
- Mohammed, A.A., Suriani, A.B. and Jabur, A.R. (2018). The enhancement of UV sensor response by zinc oxide bilayer nanocomposites film, IOP Conferences Series. *Journal of Physics*, 1003 012070.
- Muchuweni, E., Sathiaraj, T.S. and Nyakoty, H. (2017). Synthesis and characterization of zinc oxide thin films for optoelectronic applications. *Heliyon*, 3(2017): 1 – 18.
- Munoz-Aguirre, N., Martinez-Perez, L., Munoz-Aguirre, S., Florez-Herera, L.A., Hernandez, E.V. and Zelaya-Angel, O. (2019). Luminescent properties of (004) highly oriented cubic zinc blende ZnO thin films. *Materials*, 12: 1-10.
- Offor, P.O., Okorie, B.A., Ezekoye, B.A., Ezekoye, V.A. and Ezema, J.I. (2015). Chemical spray pyrolysis synthesis of zinc sulphide thin films via double precursors, *Journal of Ovonic Research*, 11(2): 73 – 77.
- Patil, G.E., Kajale, D.D., Gaikwad, V.B. and Jain, G.H. (2012). Spray pyrolysis deposition of nanostructured tin oxide thin films. *ISRN Nanotechnology*, 2012: 1 – 5.
- Qiu, J., Weng, B., Zhao, L., Chang, C., Shi, Z., Li, X., Kim, H. and Hwang, Y. (2014). Synthesis and characterization of flower-like bundles of ZnO nanosheets by surfactant-free hydrothermal process. *Journal of Nanomaterials*, 2014: 1-11.
- Rahimzadeh, M.R., Rahimzadeh, M.R. and Moghadamnia, A. (2017). Cadmium toxicity and treatment. *Caspian Journal of Internal Medicine*, 8(3): 135 – 145.
- Rajeshmon, V.G. (2013). *Prospects of Sprayed CZTS Thin Film Solar Cells from the Perspective of Material Characterization and Device Performance*. (2009). Kerala: PhD Thesis in the Department of Physics, Cochin University of

- Science and Technology, Kerala, India.
- Stamate, E. (2019). Spatially resolved optoelectronic properties of Al-doped zinc oxide thin films deposited by radio-frequency magnetron plasma sputtering without substrate heating. *Nanomaterials*, 10(14): 1 – 11.
- Stamate, E., (2019). Spatially resolved opto-electronic properties of Al-doped zinc oxide thin films deposited by radiofrequency magnetron plasma sputtering without substrate heating. *Nanomaterials*, 10(14): 1 – 11.
- Tang, G., Lin, H. and Zhang, W. (2013). The variation of optical bandgap for ZnO in films prepared by sol-gel technique. *Advances in Materials Science and Engineering*, 348601: 1–4.
- Tecaru, A., Danciu, A.I., Musat, V., Fortunato, E. and Elangovan, E. (2010). ZnO thin films prepared by spray pyrolysis. *Journal of Optoelectronics and Advanced Materials*, 12(9): 1889 – 1893.
- Thool, G.S., Singh, A.K., Singh, R.S., Gupta, A. and SuSan, M.A. (2014). Facile synthesis of flat crystal ZnO thin films by solution growth method: A micro-structural investigation, *Journal of Saudi Chemical Society*, 18(5): 712-721
- Vyas, S., Giri, P., Singh, S. and Chakrabarti, P. (2015). Comparative study of as-deposited ZnO thin films by thermal evaporation, Pulsed Laser deposition and RF sputtering methods electronic and optoelectronic applications. *Journal of Electronic Materials*, 44(2015): 3401 – 3407.
- Werner, T.T., Mudd, J.M. and Jowitt, S.M. (2015). Indium: Key issues in assessing mineral resources and long-term supply from recycling. *Applied Earth Science IMM Transactions, Section B* 124(4): 213-226